

AD-A133 519

LUMINESCENCE PROBE STUDIES OF NAFION POLYELECTROLYTES

1/1


(U) TEXAS A AND M UNIV COLLEGE STATION DEPT OF
CHEMISTRY N E PRIETO ET AL. 07 OCT 83 TR-2


UNCLASSIFIED

N00014-82-K-0612

F/G 7/4

NL

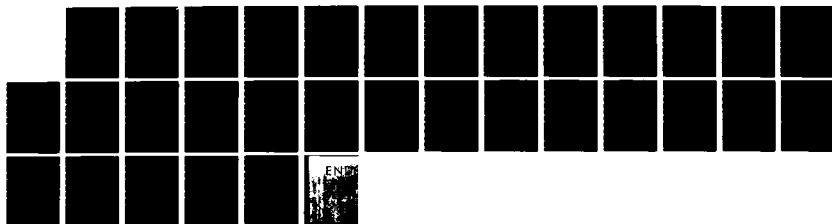

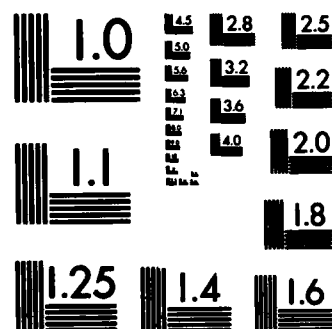

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD - A133519

OFFICE OF NAVAL RESEARCH

Contract N00014-82K-0612

Task No. NR 627-838

TECHNICAL REPORT NO. 2

Luminescence Probe Studies of Nafion Polyelectrolytes

by

Nelson E. Prieto and Charles R. Martin


Prepared for Publication

in the

Journal of the Electrochemical Society

Department of Chemistry
Texas A&M University
College Station, Texas

October 7, 1983

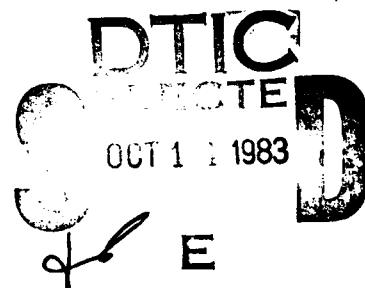

Reproduction in whole or in part is permitted for
any purpose of the United States Government

* This document has been approved for public release
and sale; its distribution is unlimited

* This statement should also appear in Item 10 of Document Control Data
- DD Form 1473. Copies of form available from cognizant contract
administrator.

83- 10 12 119

DTIC FILE COPY

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 2	2. GOVT ACCESSION NO. AD-A133519	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) LUMINESCENCE PROBE STUDIES OF NAFION POLYELECTROLYTES		5. TYPE OF REPORT & PERIOD COVERED Technical Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) Nelson E. Prieto and Charles R. Martin		8. CONTRACT OR GRANT NUMBER(s) N00014-82K-0612
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry Texas A&M University College Station, Texas 77843		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 627-838
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research 800 North Quincy Street Arlington, Virginia 22217		12. REPORT DATE October 7, 1983
		13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release; Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Presented at the 163rd Meeting of the Electrochemical Society, San Francisco, California, May 12, 1983		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Perfluorosulfonate Ionomers, Nafion, Polyelectrolytes, Ion-Containing Polymers		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) → We have recently described a procedure for dissolving perfluorosulfonate ionomer membranes. This allows, for the first time, for a study of the inherent chemical properties of the polyperfluorosulfonate molecule. Such studies of the free polyelectrolyte molecule in solution should give insight into the chemical properties of the solid state membranes obtained from these polyelectrolytes.		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 63 IS OBSOLETE
S/N 0102-LF-014-6601UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. ABSTRACT (continued)

→ The work described here focusses on investigations of the nature of the interactions between the polyperfluorosulfonates and their counterions. Clearly an electrostatic interaction is extant but because hydrophobic interactions have been implicated in various studies of perfluorosulfonate membranes, it was of interest to see if evidence for such interactions could be observed in solutions of the polyelectrolytes. Luminescence probe studies were used to investigate the nature of the interactions between the polyperfluorosulfonates and their counterions.

Accession For		
NTIS GRA&I	<input checked="checked" type="checkbox"/>	
DTIC TAB	<input type="checkbox"/>	
Unannounced	<input type="checkbox"/>	
Justification		
By		
Distribution/		
Availability Codes		
and/or		
Dist	Special	
A		



S. N 0102- LF- 014- 6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

**Luminescence Probe Studies of Nafion
Polyelectrolytes**

N. E. Prieto and C. R. Martin*

**Department of Chemistry
Texas A&M University
College Station, TX 77843**

*** Electrochemical Society Active Member**

Introduction.

Perfluorinated ionomers¹ have been used in a variety of electrochemical applications including use in chlor-alkali cells,^{2,3} water electrolyzers,⁴ zinc-bromine cells,⁵ hydrogen-halogen cells,⁶ hydrogen-oxygen fuel cells⁷ and as agents for the preparation of chemically modified electrodes.⁸ These ionomers also have a number of non-electrochemical uses.^{9,10} Because of their remarkable versatility, much current research effort is being devoted to studying the morphological and chemical properties of these ionomers.¹ We have recently described a procedure for dissolving perfluorinated ionomer membranes¹¹. This allows, for the first time, for a study of the intrinsic chemical properties of the poly(perfluorosulfonate) (PFS) molecule itself. Such studies should allow for a more thorough understanding of the chemical and perhaps the morphological features of ionomer membranes. We report at this time results of various luminescence probe studies of the polyelectrolytes obtained by dissolving the 1100 and 1200 equivalent weight versions of DuPont's Nafion¹. The primary objective of this work is to study the interactions between these anionic polyelectrolytes and their counterions.

Experimental.

Materials. Samples of 1100 and 1200 equivalent weight Nafion were kindly donated by E. I. DuPont de Nemours and Company. These were dissolved using the procedure of Martin et al.¹¹ which uses 50:50 ethanol-water as the solvent. The alcohol was removed from these solutions, immediately before use, by heating. The Na⁺ form of the polyelectrolytes (Na-PFSs) were obtained by adding carefully measured quantities of NaOH to the polymer solutions. Ru(bpy)₃Cl₂·6H₂O (bpy=2,2'-bipyridine) (G. F. Smith), 1,1'-

dimethyl-4,4'-bipyridinium dichloride hydrate (methylviologen) (Aldrich), and 1,1'-diheptyl-4,4'-bipyridinium dibromide (heptylviologen) (Aldrich) were used without further purification. Tris(2,4-pentanedione)Cobalt(III), $\text{Co}(\text{acac})_3$, (Alfa) was recrystallized from benzene, washed with diethyl ether and dried at 60°C .¹² Auramine O (4,4'-(imidocarbonyl)bis(N,N'-dimethylaniline)monohydrochloride) (the cation is abbreviated AO^+) (Sigma) was recrystallized from NaCl .¹³ 11-(3-hexyl-1-indolyl)undecyltrimethylammonium bromide (the cation is abbreviated $(6\text{-In-11})^+$)¹⁴ was donated by N. J. Turro. All other reagents were ACS reagent grade and were used without further purification. Triply distilled water was used throughout this work. The 1100 and 1200 equivalent weight versions of Nafion gave essentially identical results. Only the 1100 data is reported.

Emission Intensity and Absorbance Measurements. Emission spectra were obtained using a Spex Fluorolog 2 spectrofluorometer. $\text{Ru}(\text{bpy})_3^{2+}$, AO^+ and 6-In-11^+ were excited at 455 nm, 435 nm and 290 nm, respectively. Emission intensity was monitored at 600 nm for the $\text{Ru}(\text{bpy})_3^{2+}$ quenching studies. Absorption spectra were taken using a Beckman Model 26 spectrophotometer.

The solutions for the luminescence intensity measurements were prepared by adding aliquots of stock solutions of the polymer (1 (wt/vol) %) to $\text{Ru}(\text{bpy})_3^{2+}$ (2×10^{-5} M), AO^+ (5×10^{-5} M) or 6-In-11^+ (2×10^{-5} M) solutions in quartz cuvettes. Hamilton microliter syringes were used. The cuvette solution was mixed thoroughly after each addition of polymer solution, and intensities were corrected for dilution. The addition of salt solution or quencher to a $\text{PFS}/\text{Ru}(\text{bpy})_3^{2+}$ or PFS/AO^+ solution followed a similar procedure.

Lifetime Measurements. $\text{Ru}(\text{bpy})_3^{2+}$ lifetime measurements were done at the Center for Fast Kinetics Research at the University of Texas at Austin.

Lifetimes for $\text{Ru}(\text{bpy})_3^{2+}$ in pure water, in a solution 0.01% in H-PFS (proton form of the polyelectrolyte) and in a solution of 0.01% Na-PFS were obtained (all solutions were 2×10^{-5} M in $\text{Ru}(\text{bpy})_3^{2+}$). Solutions were degassed with prepurified nitrogen. A Quantrel YG 481 Nd:YAG Q-switched dye laser (535 nm, ca. 10 ns pulse) was used as the excitation source. Luminescence emission was monitored at 650 nm with an RCA R928 photomultiplier tube and processed with a Biomation (Gould) multichannel analyzer and a PDP-11/70 minicomputer. Metal screens were used to attenuate the incident laser intensity.

Results and Discussion.

The Luminescence Probe Studies. As noted above, the primary objective of this work is to study the nature of the interactions between the Nafion polyelectrolytes and their counterions. Clearly an electrostatic interaction^{15a} will be present, but because hydrophobic interactions^{15b} have been implicated in various studies of Nafion membranes,^{8,16,17} it was of interest to see if evidence for such interactions could be observed in solutions of the polyelectrolytes. Luminescence probe studies have been shown to be quite effective at characterizing polyion-counterion interactions in other polyelectrolyte systems.¹⁸⁻²⁴ Two types of luminescence probe experiments were used here. The first involved studies of the effect of addition of the PFSs on the luminescence emission intensities of various cationic probes in aqueous solution. Three structural diverse probes, 6-In-11⁺^{14,22,23}, $\text{Ru}(\text{bpy})_3^{2+}$ and AO^+ ²⁴ were chosen for these studies. 6-In-11⁺ was chosen because the effect of solvent polarity on its emission characteristics are dramatic and well characterized^{14,22,23} and because it has been used to study polyion-counterion interactions in poly(styrene-

sulfonate)(PSS).²³ $\text{Ru}(\text{bpy})_3^{2+}$ was chosen because Lee and Meisel have suggested that hydrophobic interactions between this ion and the fluorocarbon chain material occur in 1200 equivalent weight Nafion membranes.¹⁶ AO^+ was chosen because it has proved to be ideally suited for studying polymer-probe interactions.²⁴

The second set of luminescence probe experiments involved studies of the effect of the PSSs on the rates of quenching of $\text{Ru}(\text{bpy})_3^{2+}$ by various electron transfer quenching agents. $\text{Ru}(\text{bpy})_3^{2+}$ was chosen for these studies because it strongly binds to the PSSs (vide infra) and because its luminescence in aqueous solution has been well characterized.²⁵

Luminescence Intensity Studies. Figure 1 shows the effect of addition of an aqueous solution of Na-PSS (1 wt./vol.%) on the emission spectra of 6-In-11⁺. A pronounced blueshift in the position of the emission spectrum is observed (wavelength of maximum emission intensity, λ_{max} , in water is 374 nm, λ_{max} in Nafion solution is 356 nm). A blueshift in the emission of a probe (relative to water) is often indicative of a more hydrophobic environment for the probe.²⁶ (The photochemical mechanism for such a shift is discussed by Brand and Gohlke.²⁶) The observed blueshift, then, suggests that Nafion is engaging in hydrophobic interactions with 6-In-11⁺. In this type of luminescence probe study, however, it is desirable to compare the emission of the probe from the unknown environment with its emission spectrum from some well characterized environment. It is known that PSS can engage in strong hydrophobic interactions with its counterions.^{18,23} Turro and Okubo observed a pronounced blueshift in the emission of 6-In-11⁺ from aqueous solutions of PSS, which they attributed to hydrophobic binding of this probe by PSS.²³ The similarity in the responses of this probe to

the unknown (Nafion) and standard (PSS) environments adds further evidence for hydrophobic interactions between 6-In-11⁺ and Nafion.

In addition to the shift in λ_{max} , a decrease in emission intensity, with the initial additions of Na-PFS, is observed (Figure 1b) followed by a gradual increase in intensity with further additions (Figure 1c). Similar results were obtained by Turro and Okubo in their investigations of Na-PSS.²³ They suggest that quenching by trace impurities present in the polymer solution may account for the initial decrease in emission intensity.²³

Further evidence for a strong hydrophobic component to the interaction between 6-In-11⁺ and PFS is obtained from studies of 6-In-11⁺ absorption spectra. As shown in Figure 2, the absorbance at 290 nm increases as Na-PFS is added to a solution of 6-In-11⁺. Turro has shown that the absorbance for this probe increases as the polarity of the environment around the probe decreases;^{22,23} furthermore, a similar increase in absorbance was observed with PSS.²³ Figure 2 shows excitation spectra obtained with the fluorometer, but true absorbance spectra (obtained with the spectrophotometer) gave identical results. Finally, it is important to note that while the data shown in Figures 1 and 2 refer specifically to the Na⁺ form of PFS, essentially identical results were obtained with the proton form. These studies clearly show that 6-In-11⁺ engages in strong hydrophobic interactions with the PFSs.

Figure 3 shows the effect of concentration of Na-PFS (expressed as the molarity of -SO₃⁻ sites) on the intensity of emission by Ru(bpy)₃^{2+*}. Emission intensity is expressed as the ratio I/I° where I° is the intensity in pure water and I is the intensity after addition of an increment of the Na-PFS solution.²¹ Emission intensity increases with increasing concentra-

tion of PFS until a stoichiometrically equivalent amount of -SO_3^- sites have been added to the solution (i.e., until $2 \times [\text{-SO}_3^-] = [\text{Ru}(\text{bpy})_3^{2+}]$). This increase in intensity is not due to some polymer-induced change in bulk concentration of the $\text{Ru}(\text{bpy})_3^{2+}$ because the absorption spectrum (corrected for dilution) is unaffected by the presence of PFS; nor is this intensity increase due merely to a change in the shape of the emission band because an analogous plot of the areas under the emission bands gives an identical curve. When greater than stoichiometric amounts of PFS are added, a leveling in emission intensity is observed (Figure 3).

The leveling of the emission intensity at the stoichiometric equivalence point implicates a role for electrostatic interactions in the observed increase in emission intensity. However, if a hydrophilic, divalent metal ion (e.g., Mg^{2+}) is added to a $\text{Ru}(\text{bpy})_3^{2+}$ /PFS solution, a huge excess of the hydrophilic ion is required to return I/I° back to 1 (Figure 4, the ratio (moles Mg^{2+} /moles $\text{Ru}(\text{bpy})_3^{2+}$) to make I/I° 1 is ca. 1000). If the increase in emission intensity (Figure 3) resulted from purely electrostatic interactions, the ability of Mg^{2+} to replace $\text{Ru}(\text{bpy})_3^{2+}$ as the counterion of the polyelectrolyte would not be so severely retarded, that is, one might expect the ratio (moles Mg^{2+} /moles $\text{Ru}(\text{bpy})_3^{2+}$) required to make I/I° ca. 1 to be close to unity. Given the hydrophobic nature of $\text{Ru}(\text{bpy})_3^{2+}$, the results in Figure 4 indicate that there is also a strong hydrophobic interaction between this counterion and the PFSs. The binding of $\text{Ru}(\text{bpy})_3^{2+}$ to the PFSs is via a concerted hydrophobic/electrostatic interaction.

When $\text{Ru}(\text{bpy})_3^{2+}$ is used as a luminescence probe of hydrophilic polyanion where only electrostatic interactions are extant, emission intensity does not change with the concentration of the polyanion.²⁷ This suggests

that the increase in emission intensity in Figure 3 is caused by the hydrophobic part of the interaction. Kurimura et al. saw a similar increase in emission intensity when PSS was added to a $\text{Ru}(\text{bpy})_3^{2+}$ solution and they also concluded that this increase was due to hydrophobic interactions.²¹ A consideration of the effect of water on the non-radiative rate constant provides a possible explanation for the observed increases in $\text{Ru}(\text{bpy})_3^{2+}$ emission intensity. As recently noted by Caspar and Meyer,²⁸ water is particularly effective at promoting non-radiative decay in $\text{Ru}(\text{bpy})_3^{2+}$. It seems likely, then, that any interaction which shields $\text{Ru}(\text{bpy})_3^{2+}$ from water will increase its quantum yield (the radiative rate constant is relatively insensitive to solvent²⁸). Since it is the incompatibility of water and the hydrophobic solute which promotes hydrophobic bonding,^{15b} it is reasonable to assume that when bound to PFS, $\text{Ru}(\text{bpy})_3^{2+}$ minimizes its contact with water. Therefore, a quantum yield increase would be expected.

The final luminescence probe used was AO^+ . In nonviscous solvents electronic excitation energy in AO^+ is dissipated as heat via rotation of its phenyl rings.²⁴ For this reason, AO^+ does not fluoresce in water (Figure 5) or other non-viscous solvents.²⁴ Binding of AO^+ to polyanions hinders phenyl ring rotation and fluorescence can be observed.²⁴ Figure 5 shows that Na-PFS can induce fluorescence in AO^+ . As was the case with $\text{Ru}(\text{bpy})_3^{2+}$, fluorescence intensity is proportional to $[-\text{SO}_3^-]$ until a stoichiometrically equivalent quantity of polymer is added. Furthermore, huge excesses (ca. 1000 fold) of Na^+ are required to return the emission intensity to background levels, indicating that AO^+ also binds via a concerted hydrophobic/electrostatic interaction.

Quenching Studies. It is well known that quenching reactions between an electronically excited cation and a cationic quencher are accelerated in

the presence of a polyanion.^{19,27,29} This acceleration is due to the concentration of the cations in the domain around the polyion chains (i.e., the local concentrations of both emitter and quencher are higher than the bulk concentrations).^{19,27,29} It was of interest to see if acceleration of quenching reactions between cationic quenchers and $\text{Ru}(\text{bpy})_3^{2+*}$ could be observed in the presence of the PFSs. Furthermore, given the strongly hydrophobic nature of the PFSs (vide supra), it was of particular interest to see if a contribution from hydrophobic interactions¹⁸ could be discerned in any acceleration observed.

Quenching rate constants were determined using the emission intensity form of the Stern-Volmer equation.³⁰ Typical Stern-Volmer plots are shown in Figure 6. We have obtained apparent quenching rate constants from such plots for hydrophilic cation, hydrophobic cation, and neutral quenchers in the presence of both Na-PFS and H-PFSs (Table 1). Measured $\text{Ru}(\text{bpy})_3^{2+*}$ lifetimes of 640 ± 10 ns (Na-PFS) and 590 ± 10 ns (H-PFS) were used for calculation of these rate constants. They are called apparent quenching rate constants because they have been calculated assuming the bulk quencher concentrations. To obtain real quenching rate constants, the values shown in Table 1 would have to be normalized as described by Meisel et al.¹⁹ Since it is the magnitude of the rate constant enhancement which is of interest here, normalization was not attempted.

Table 1 shows that quenching rate constants are enhanced for all of the cationic quenchers. The amount of enhancement can be described quantitatively by the enhancement factor, α , which is the ratio of the apparent rate constant in the presence of the polymer to the rate constant observed in pure water. Enhancement factors (Table 2) for the hydrophobic cations (methylviologen and heptylviologen) are seven to ten times larger than the

enhancement factors for the hydrophilic cations. As in the previous set of experiments, these data show that hydrophobic interactions can play an important role in the binding of counterions to the PFSs. Again, however, the importance of the electrostatic component of the interaction is demonstrated because quenching by neutral $\text{Co}(\text{acac})_3$ is not changed appreciably by the presence of the polyanion. As was indicated by the data obtained in the intensity studies, a concerted hydrophobic/electrostatic interaction is required to produce strong binding.

Conclusions. This work has shown that strong binding to the Nafion polyelectrolytes occurs when both electrostatic and hydrophobic interactions are possible. This helps to explain why a Nafion film on an electrode surface retains hydrophobic counterions (e.g., $\text{Ru}(\text{bpy})_3^{2+}$, MV^{2+})⁸ when the film is immersed in a solution containing high (e.g., 0.1 M) salt concentrations and none of the hydrophobic ion. Nafion shows very different selectivity than the polyelectrolytes investigated by Anson³¹ which apparently bind only via electrostatic interactions. We are currently investigating ion exchange selectivity in cationic analogs of Nafion to see if hydrophobically driven ion exchange is a general phenomenon.

This work also raises important points concerning the transport properties of Nafion. The permeability of a material to a solute species is proportional to the product of the partition constant and the diffusion coefficient for that species in the material. In most of the electrochemical applications of Nafion, high permeability to cations is desired. Because of the affinity of the polymer for hydrophobic cations (i.e., high partition constant), these ions could show higher permeabilities than smaller alkali metal ions, if the membrane is in contact with a solution con-

taining both types of cations. Finally, these data corroborate results obtained previously in this laboratory which showed that rates of ionic diffusion through Nafion films can be affected by hydrophobic interactions.³²

Acknowledgements. This work was supported in part by the Office of Naval Research. Acknowledgement is also made to the donors of the Petroleum Research Fund, administered by the American Chemical Society, for partial support of this work. The authors would like to thank M. A. J. Rodgers and S. Atherton of the Center for Fast Kinetics Research, University of Texas at Austin for assisting with the lifetime measurements and for valuable discussions.

Table 1. Apparent second order rate constants ($M^{-1}s^{-1}$) for quenching of $Ru(bpy)_3^{2+}$ emission by various quenchers. Effect of the PFSs on the rate constants.

Media	Quenchers				
	Cu^{2+}	Fe^{3+}	MV^{2+a}	HV^{2+b}	$Co(acac)_3^c$
Water	$7.7 \times 10^7^d$	$2.1 \times 10^8^e$	$4.5 \times 10^8^f$	$4.2 \times 10^8^g$	$1.1 \times 10^9^h$
H-PFS ⁱ	2.4×10^9	2.2×10^9	1.5×10^{11}	9.7×10^{10}	1.5×10^9
Na-PFS ⁱ	3.9×10^9		4.5×10^{11}		

^a Methylviologen

^b Heptylviologen

^c acac = acetylacetone

^d Meisel et al., J. Am. Chem. Soc., 100, 117 (1978).

^e Reference 19

^f Reference 16

^g M.A.J. Rodgers and J.C. Becker, J. Phys. Chem., 84, 2762 (1980).

^h Reference 12

ⁱ Solution was $2 \times 10^{-5}M$ in $Ru(bpy)_3^{2+}$ and 0.05% in polymer.

Table 2. H-PFS induced enhancement factors, α (α = apparent rate constant in the presence of polymer divided by pure water rate constant) for various quenchers.^a

Quencher	Cu^{2+}	Fe^{3+}	MV^{2+}	HV^{2+}	$\text{Co}(\text{acac})_3$
α	31	10	330	230	1.4

^a See Table 1.

References.

1. A. Eisenberg and H. L. Yeager, Eds., Perfluorinated Ionomer Membranes, ACS Symposium Series No. 180, ACS, Washington, D.C. (1982) and references therein.
2. W. Grot, Chem.-Ing.-Tech., 50, 299 (1978).
3. W. Grot, G. E. Munn, and P. M. Walmsley, Presented to the 141st National Meeting of the Electrochemical Society, Houston, TX, May 7-11 (1972).
4. R. S. Yeo, J. McBreen, G. Kissel, F. Kulesa, and S. Srinivasan, J. Appl. Electrochem., 10, 741 (1980).
5. F. G. Will, this Journal, 126, 36 (1979).
6. R. S. Yeo and D.-T. Chin, this Journal, 127, 549 (1980).
7. A. B. LaConti, A. R. Fragala, and J. R. Boyack, in, J.D.E. McIntyre, S. Srinivasan and F. G. Will, Eds., Proceedings of the Symposium on Electrode Materials and Processes for Energy Conversion and Storage, the Electrochemical Society, Inc., N.J., 1977, p. 354.
8. C. R. Martin, I. Rubinstein, and A. J. Bard, J. Am. Chem. Soc., 104, 4817 (1982) and references therein.
9. G. A. Olah, G. K. S. Prakash and J. Sommer, Science, 206, 13 (1979).
10. H. L. Yeager and A. Steck, Anal. Chem., 51, 862 (1979).
11. C. R. Martin, T. A. Rhoades, and J. A. Ferguson, Anal. Chem., 54, 1639 (1982).
12. D. Meyerstein, J. Rabani, M. S. Matheson, and D. Meisel, J. Phys. Chem., 82, 1879 (1978).
13. R. H. Conrad, J. Heitz, and L. Brand, Biochem., 9, 1540 (1970).
14. N. E. Schore and N. J. Turro, J. Am. Chem. Soc., 97, 2488 (1975).
15. (a) Reviews of the nature and extent of electrostatic interactions between polyelectrolytes and their counterions are given in E. Selegny, Ed., Polyelectrolytes, D. Reidel Pub. Co., Dordrecht, Holland, 1974.
(b) A brief review of hydrophobic interactions is given by J. Fietelson, in J. A. Marinsky and Y. Marcus, Eds., Ion Exchange and Solvent Extraction, Vol. 2, Marcel Dekker, NY, 1969.
16. P. C. Lee and D. Meisel, J. Am. Chem. Soc., 102, 5477 (1980).
17. C. R. Martin and H. Freiser, Anal. Chem., 53, 902 (1981).
18. N. J. Turro and T. Okubo, J. Phys. Chem., 86, 1535 (1982).

19. D. Meisel, J. Rabani, D. Meyerstein and M. S. Matheson, *J. Phys. Chem.*, 82, 985 (1978).
20. T. Okubo and N. J. Turro, *J. Phys. Chem. Soc.*, 85, 4034 (1981).
21. Y. Kurimura, H. Yokota, K. Shigehara, and E. Tsuchida, *Bull. Chem. Soc. Jpn.*, 55, 55 (1982).
22. N. J. Turro, Y. Tanimoto, and G. Gabor, *Photochem. Photobiol.*, 31, 527 (1980).
23. N. J. Turro and T. Okubo, *J. Am. Chem.*, 104, 2985 (1982).
24. G. Oster and Y. Nishijima, *Fortschr. Hochpolym.-Forsch.*, 3, 313 (1964).
25. K. Kalyanasundaram, *Coord. Chem. Rev.*, 46, 159 (1982).
26. L. Brand and J. R. Gohlke, *Ann. Rev. Biochem.*, 41, 843 (1972).
27. D. Meisel and M. S. Matheson, *J. Am. Chem. Soc.*, 99, 6577 (1977).
28. J. V. Caspar and T. J. Meyer, *J. Am. Chem. Soc.*, 105, 5583 (1983).
29. H. Morawetz, *Acc. Chem. Res.*, 3, 354 (1970).
30. C. A. Parker, Photoluminescence of Solutions, Elsevier Pub. Co., Amsterdam, 1968, pp 71-74.
31. N. Oyama and F. C. Anson, *this Journal*, 127, 247 (1980).
32. C. R. Martin and K. A. Dollard, *J. Electroanal. Chem.*, in press.

Figure Captions.

Figure 1. Effect of addition of Na-PFS on fluorescence spectra for 6-In-11⁺ (2×10^{-5} M). A. No Nafion added. B. After addition of Na-PFS solution. 3.79×10^{-8} moles of $-\text{SO}_3^-$ sites added. C. After addition of more Na-PFS solution. 5.05×10^{-7} moles of $-\text{SO}_3^-$ sites added.


Figure 2. Excitation spectra of 6-In-11⁺ (2×10^{-5} M, monitored at 374 nm). A. No Nafion added. B. After addition of Na-PFS solution. 7.26×10^{-8} moles of $-\text{SO}_3^-$ sites added. C. After addition of more Na-PFS solution. 1.99×10^{-7} moles of $-\text{SO}_3^-$ sites added.


Figure 3. Dependence of $\text{Ru}(\text{bpy})_3^{2+}$ luminescence emission intensity on concentration of Na-PFS. $[\text{Ru}(\text{bpy})_3^{2+}] = 2 \times 10^{-5}$ M. $\lambda_{\text{EX}} = 455$ nm, $\lambda_{\text{EM}} = 610$ nm.


Figure 4. Effect of addition of MgSO_4 on emission intensity of $\text{Ru}(\text{bpy})_3^{2+}$ from a $\text{Ru}(\text{bpy})_3^{2+}$ /Na-PFS solution. 2×10^{-8} moles $\text{Ru}(\text{bpy})_3^{2+}$, 6×10^{-8} moles Nafion $-\text{SO}_3^-$ sites (see Figure 3).


Figure 5. Fluorescence spectra of AO^+ as a function of concentration of Na-PFS ($[\text{AO}^+] = 5 \times 10^{-5}$ M, $\lambda_{\text{EX}} = 435$ nm). A. No Na-PFS. B. 9×10^{-9} moles of $-\text{SO}_3^-$ sites. C. 1.8×10^{-8} moles $-\text{SO}_3^-$ sites. D. 2.7×10^{-8} moles $-\text{SO}_3^-$ sites. E. 3.6×10^{-8} moles $-\text{SO}_3^-$ sites.


Figure 6. Typical Stern-Volmer plots for quenching of PFS-bound $\text{Ru}(\text{bpy})_3^{2+}$ by various quenchers. $[\text{Ru}(\text{bpy})_3^{2+}] = 2 \times 10^{-5}$ M, $[\text{Na-PFS}] = 0.05\%$.

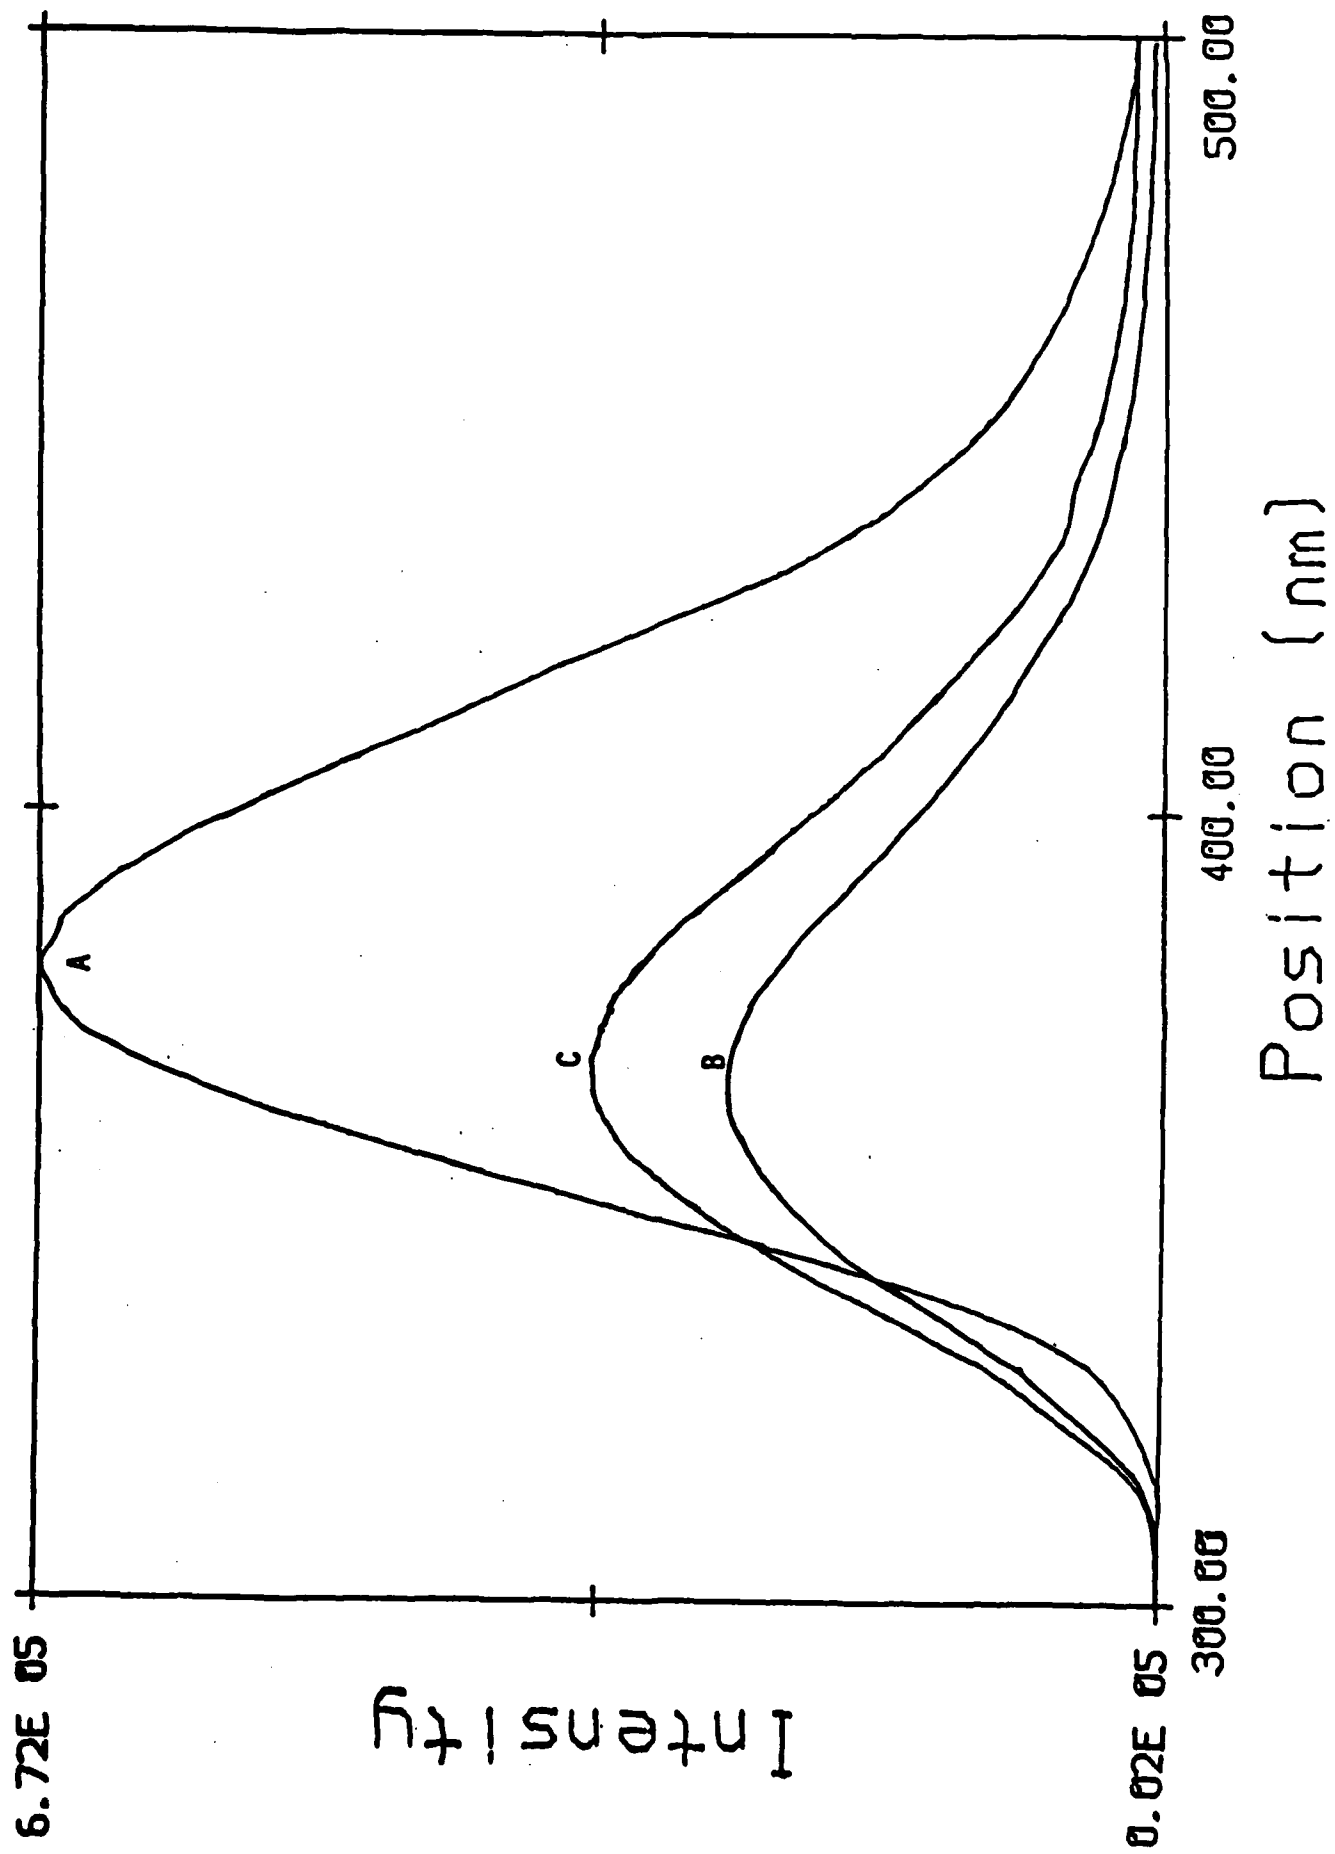

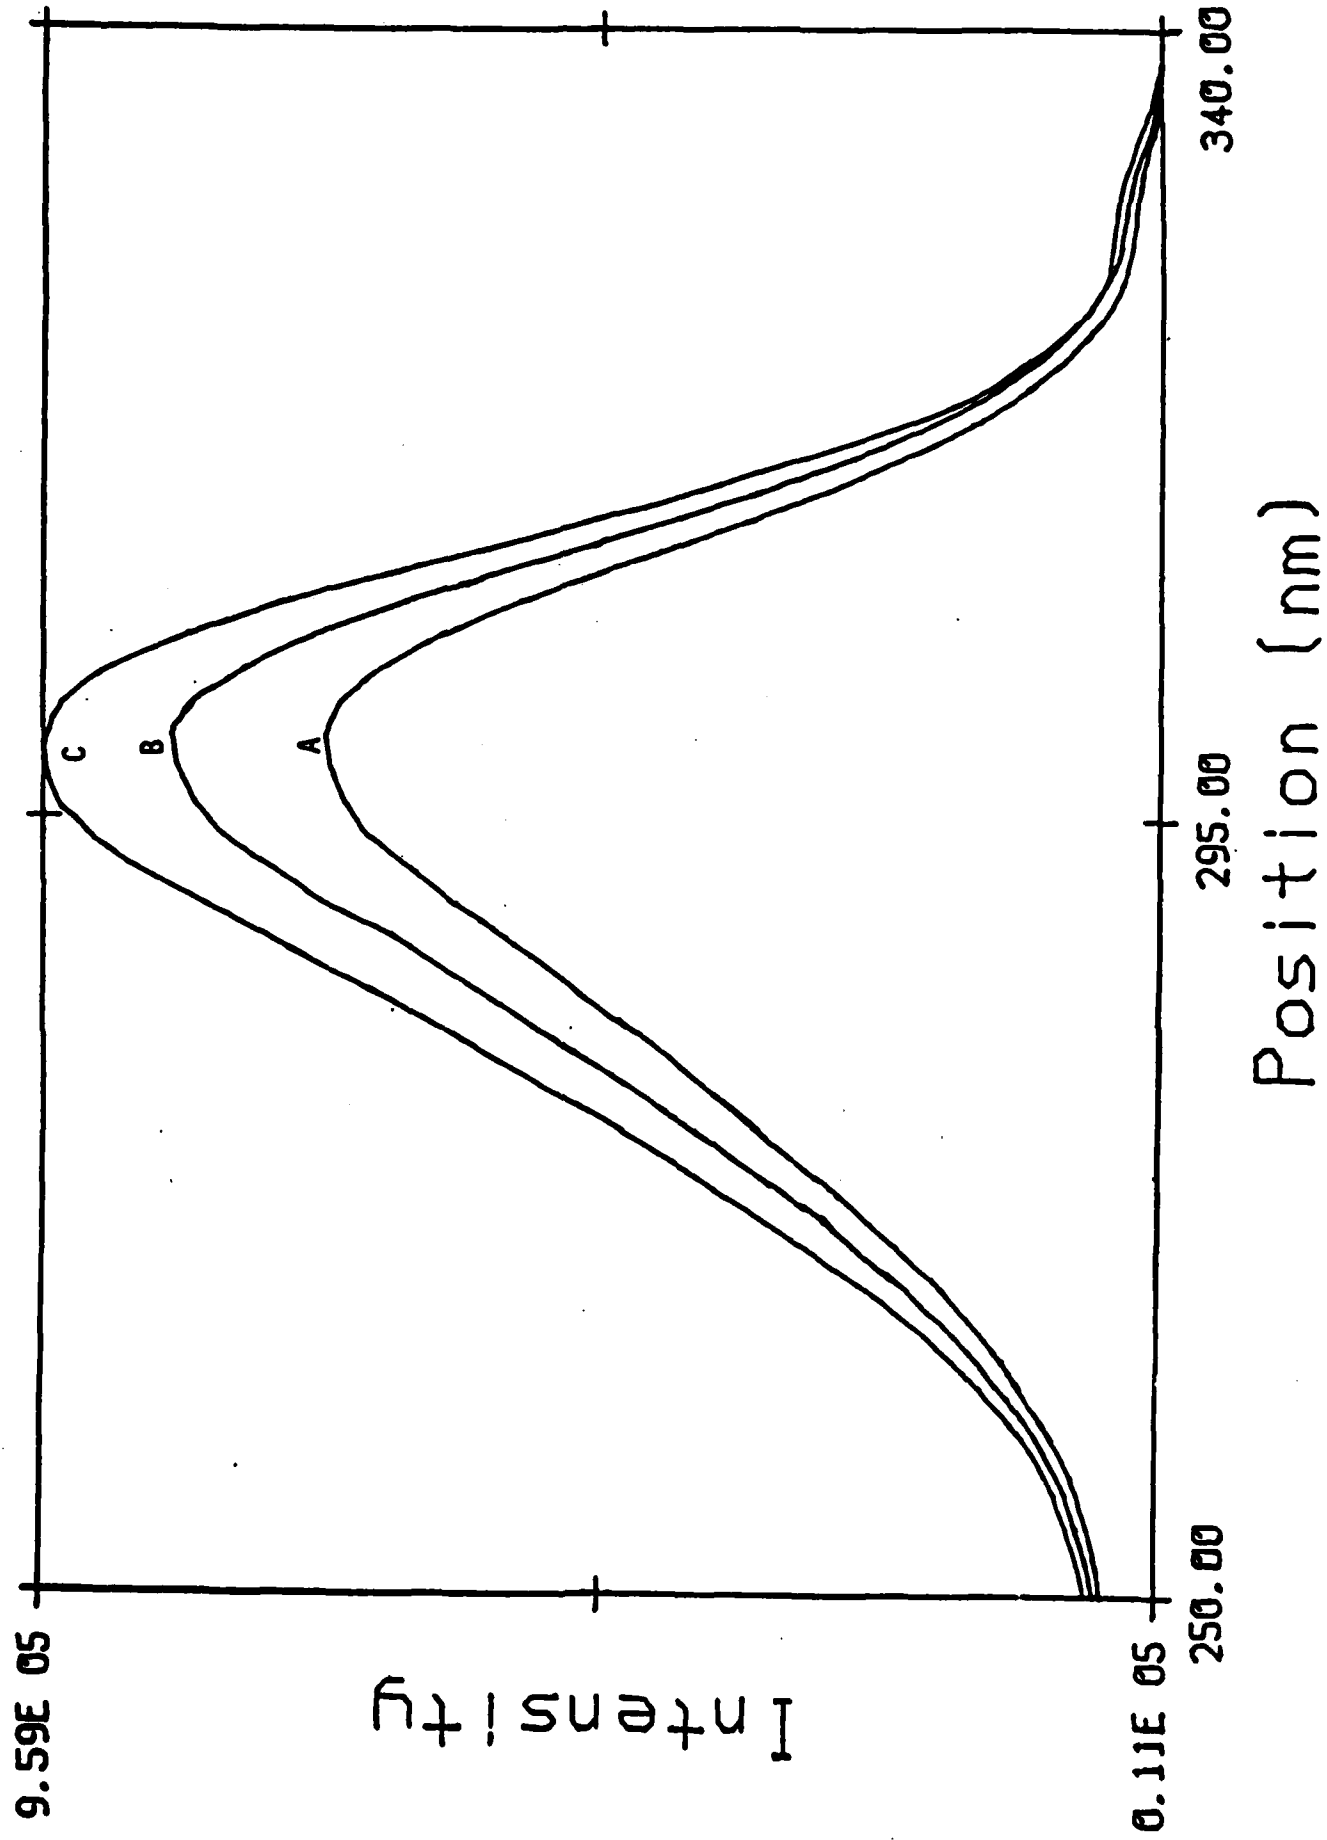


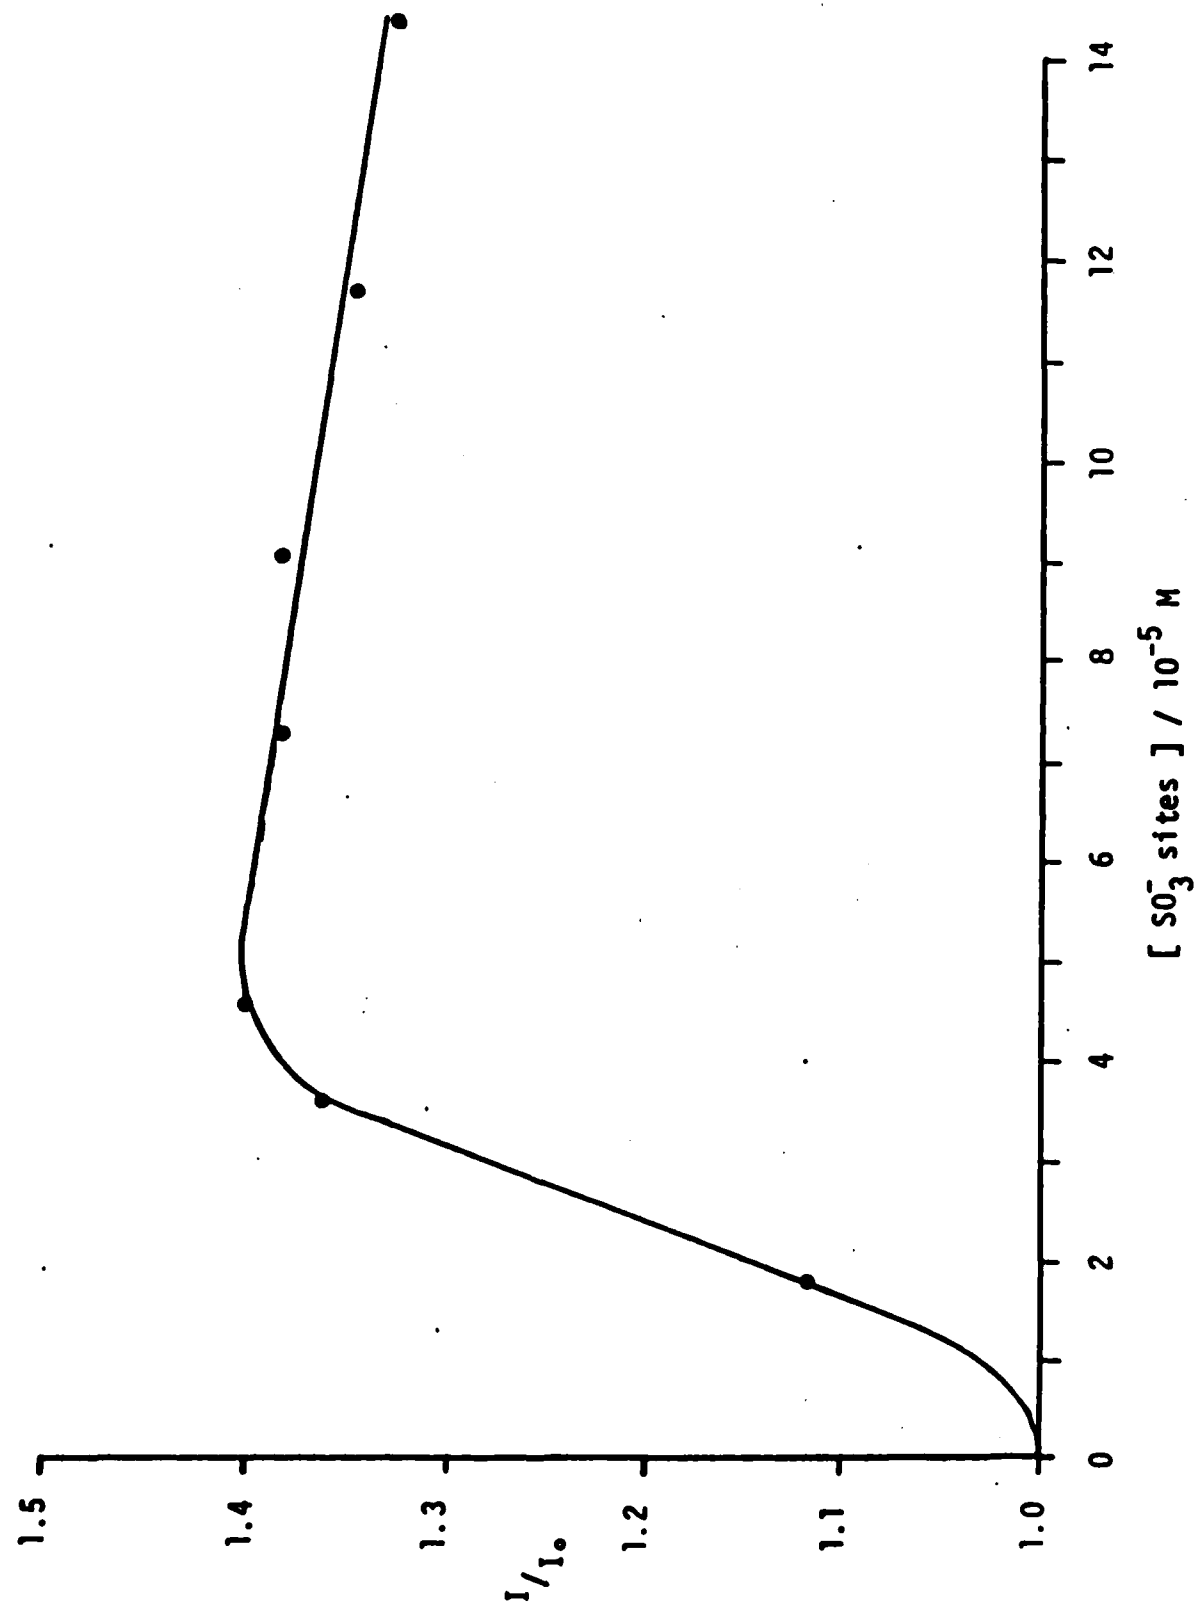

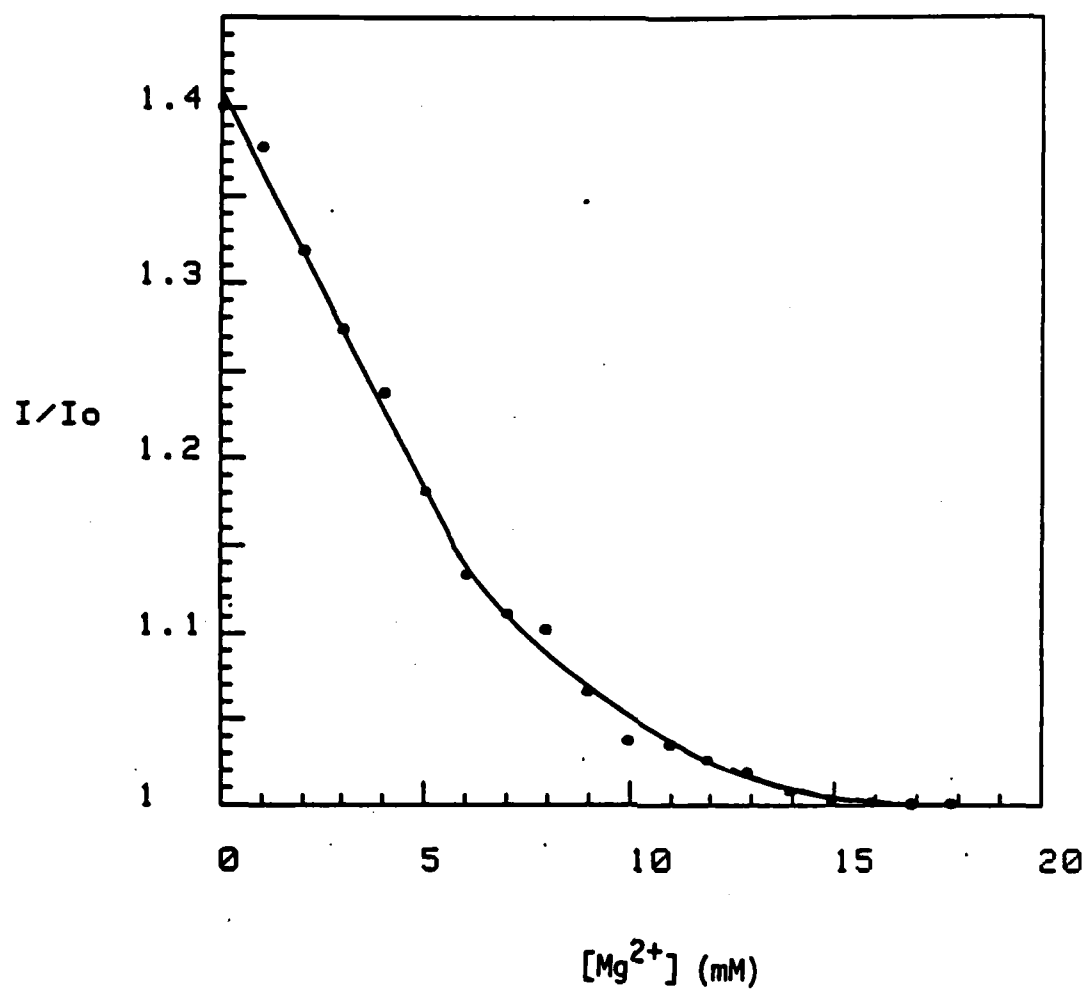

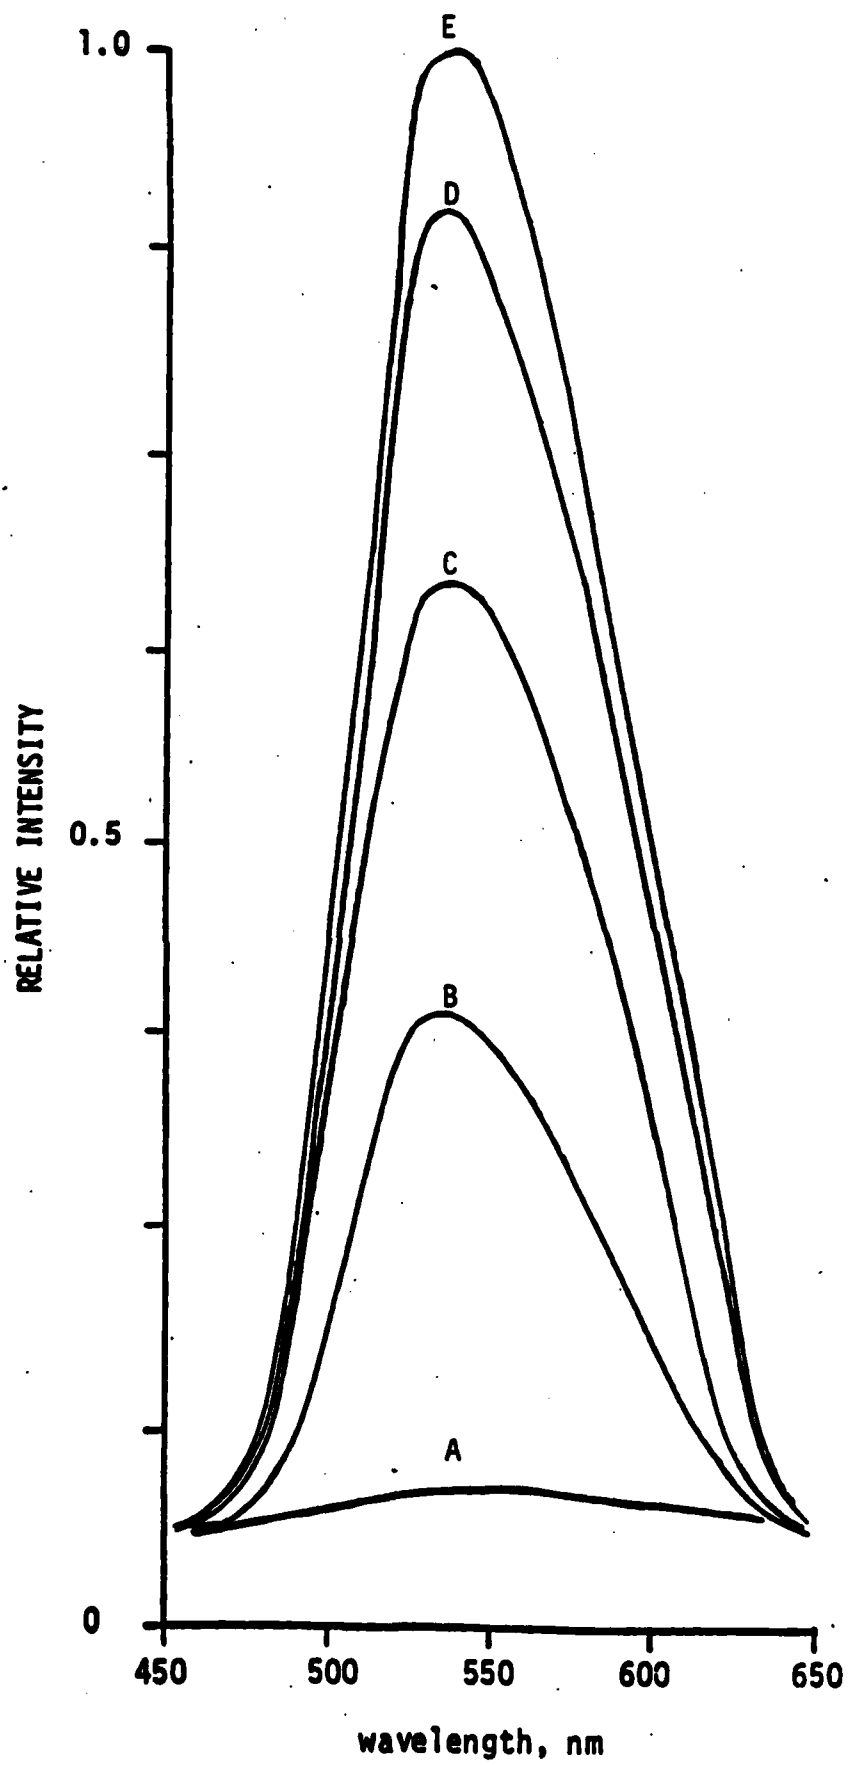

$[\text{Co}(\text{acac})_3] \times 10^{-4} \text{M}$

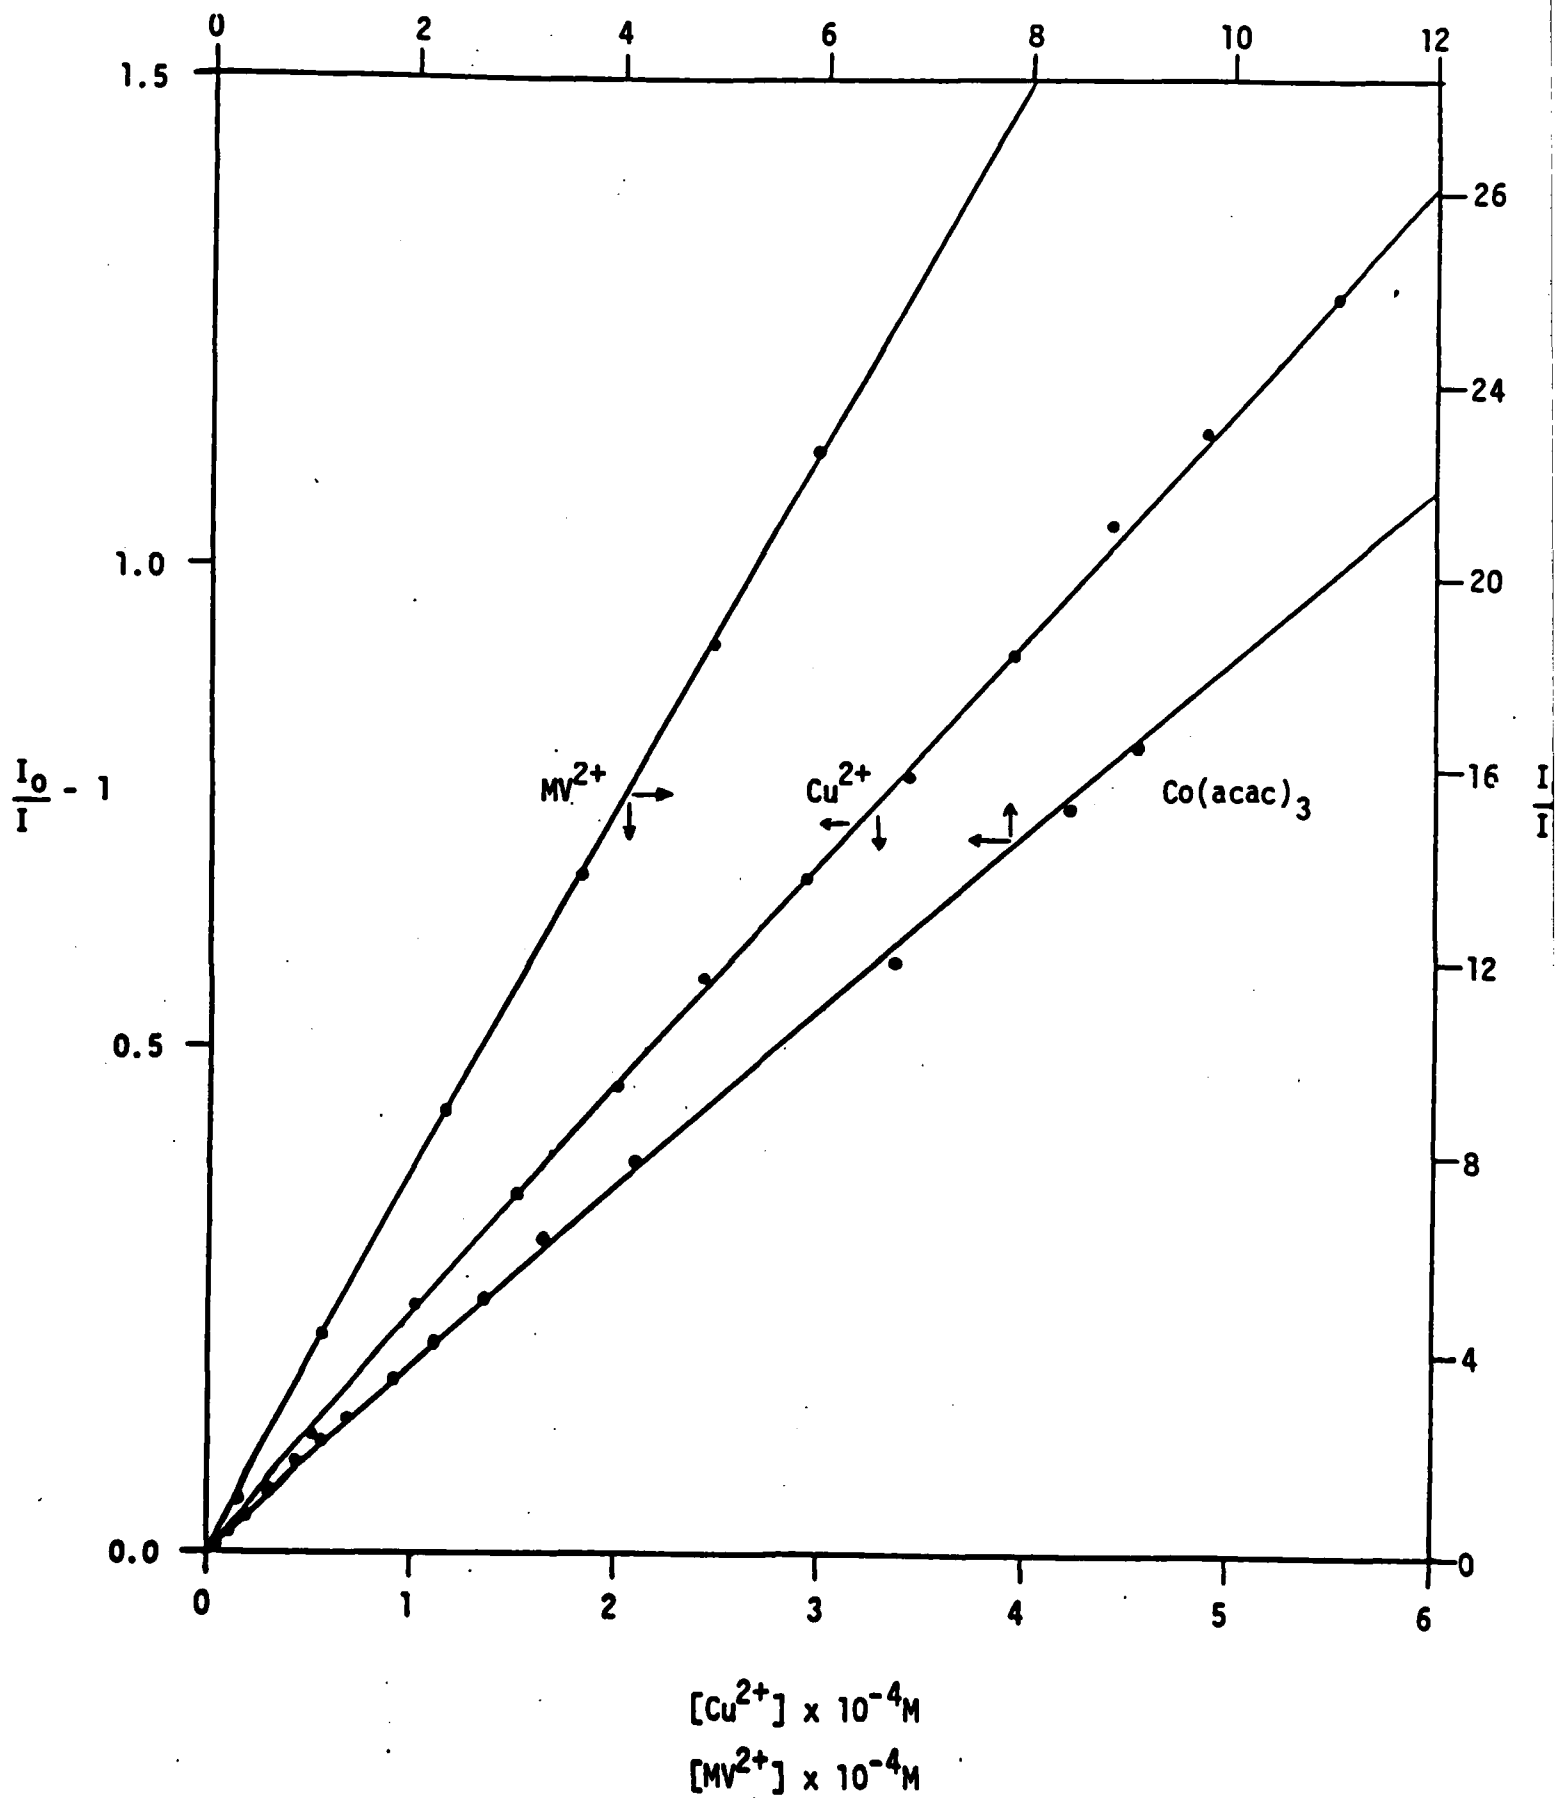

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No.</u> <u>Copies</u>		<u>No</u> <u>Copi</u>
Office of Naval Research Attn: Code 413 800 North Quincy Street Arlington, Virginia 22217	2	Naval Ocean Systems Center Attn: Mr. Joe McCartney San Diego, California 92152	1
ONR Pasadena Detachment Attn: Dr. R. J. Marcus 1030 East Green Street Pasadena, California 91106	1	Naval Weapons Center Attn: Dr. A. B. Amster, Chemistry Division China Lake, California 93555	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Department of the Navy Washington, D.C. 20360	1	Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Dean William Tolles Naval Postgraduate School Monterey, California 93940	1
Dr. Fred Saalfeld Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
U.S. Army Research Office Attn: CRD-AA-IP P. O. Box 12211 Research Triangle Park, N.C. 27709	1	Naval Ship Research and Development Center Attn: Dr. G. Bosmajian, Applied Chemistry Division Annapolis, Maryland 21401	1
Mr. Vincent Schaper DTNSRDC Code 2803 Annapolis, Maryland 21402	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1	Mr. A. M. Anzalone Administrative Librarian PLASTEC/ARRADCOM Bldg 3401 Dover, New Jersey 07801	1

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. Paul Delahay Department of Chemistry New York University New York, New York 10003	1	Dr. P. J. Hendra Department of Chemistry University of Southampton Southampton SOO 5NH United Kingdom	1
Dr. E. Yeager Department of Chemistry Case Western Reserve University Cleveland, Ohio 41106	1	Dr. Sam Perone Chemistry & Materials Science Department Laurence Livermore National Lab. Livermore, California 94550	1
Dr. D. N. Bennion Department of Chemical Engineering Brigham Young University Provo, Utah 84602	1	Dr. Royce W. Murray Department of Chemistry University of North Carolina Chapel Hill, North Carolina 27514	1
Dr. R. A. Marcus Department of Chemistry California Institute of Technology Pasadena, California 91125	1	Naval Ocean Systems Center Attn: Technical Library San Diego, California 92152	1
Dr. J. J. Auburn Bell Laboratories Murray Hill, New Jersey 07974	1	Dr. C. E. Mueller The Electrochemistry Branch Materials Division, Research and Technology Department Naval Surface Weapons Center White Oak Laboratory Silver Spring, Maryland 20910	1
Dr. Adam Heller Bell Laboratories Murray Hill, New Jersey 07974	1	Dr. G. Goodman Johnson Controls 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. T. Katan Lockheed Missiles and Space Co., Inc. P. O. Box 504 Sunnyvale, California 94088	1	Dr. J. Boechler Electrochimica Corporation Attn: Technical Library 2485 Charleston Road Mountain View, California 94040	1
Dr. Joseph Singer, Code 302-1 NASA-Lewis 21000 Brookpark Road Cleveland, Ohio 44135	1	Dr. P. P. Schmidt Department of Chemistry Oakland University Rochester, Michigan 48063	1
Dr. B. Brummer EIC Incorporated 55 Chapel Street Newton, Massachusetts 02158	1		
Library P. R. Mallory and Company, Inc. Northwest Industrial Park Burlington, Massachusetts 01803	1		

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. H. Richtol Chemistry Department Rensselaer Polytechnic Institute Troy, New York 12181	1	Dr. R. P. Van Duyne Department of Chemistry Northwestern University Evanston, Illinois 60201	1
Dr. A. B. Ellis Chemistry Department University of Wisconsin Madison, Wisconsin 53706	1	Dr. B. Stanley Pons Department of Chemistry University of Alberta Edmonton, Alberta CANADA T6G 2G2	1
Dr. M. Wrighton Chemistry Department Massachusetts Institute of Technology Cambridge, Massachusetts 02139		Dr. Michael J. Weaver Department of Chemistry Michigan State University East Lansing, Michigan 48824	1
Larry E. Plew Naval Weapons Support Center Code 30736, Building 2906 Crane, Indiana 47522	1	Dr. R. David Rauh EIC Corporation 55 Chapel Street Newton, Massachusetts 02158	1
S. Ruby DOE (STOR) 600 E Street Providence, Rhode Island 02192	1	Dr. J. David Margerum Research Laboratories Division Hughes Aircraft Company 3011 Malibu Canyon Road Malibu, California 90265	1
Dr. Aaron Wold Brown University Department of Chemistry Providence, Rhode Island 02192	1	Dr. Martin Fleischmann Department of Chemistry University of Southampton Southampton 509 5NH England	1
Dr. R. C. Chudacek McGraw-Edison Company Edison Battery Division Post Office Box 28 Bloomfield, New Jersey 07003	1	Dr. Janet Osteryoung Department of Chemistry State University of New York at Buffalo Buffalo, New York 14214	1
Dr. A. J. Bard University of Texas Department of Chemistry Austin, Texas 78712	1	Dr. R. A. Osteryoung Department of Chemistry State University of New York at Buffalo Buffalo, New York 14214	1
Dr. M. M. Nicholson Electronics Research Center Rockwell International 3370 Miraloma Avenue Anaheim, California	1		

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. Donald W. Ernst Naval Surface Weapons Center Code R-33 White Oak Laboratory Silver Spring, Maryland 20910	1	Mr. James R. Moden Naval Underwater Systems Center Code 3632 Newport, Rhode Island 02840	1
Dr. R. Nowak Naval Research Laboratory Code 6130 Washington, D.C. 20375	1	Dr. Bernard Spielvogel U. S. Army Research Office P. O. Box 12211 Research Triangle Park, NC 27709	1
Dr. John F. Houlihan Shenango Valley Campus Pennsylvania State University Sharon, Pennsylvania 16146	1	Dr. Denton Elliott Air Force Office of Scientific Research Bolling AFB Washington, D.C. 20332	1
Dr. D. F. Shriver Department of Chemistry Northwestern University Evanston, Illinois 60201	1	Dr. David Aikens Chemistry Department Rensselaer Polytechnic Institute Troy, New York 12181	1
Dr. D. H. Whitmore Department of Materials Science Northwestern University Evanston, Illinois 60201	1	Dr. A. P. B. Lever Chemistry Department York University Downsview, Ontario M3J1P3 Canada	1
Dr. Alan Bewick Department of Chemistry The University Southampton, SO9 5NH England		Dr. Stanislaw Szpak Naval Ocean Systems Center Code 6343 San Diego, California 95152	1
Dr. A. Himy NAVSEA-5433 NC #4 2541 Jefferson Davis Highway Arlington, Virginia 20362		Dr. Gregory Farrington Department of Materials Science and Engineering University of Pennsylvania Philadelphia, Pennsylvania 19104	
Dr. John Kincaid Department of the Navy Strategic Systems Project Office Room 901 Washington, D.C. 20376		Dr. Bruce Dunn Department of Engineering & Applied Science University of California Los Angeles, California 90024	

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No.</u> <u>Copies</u>	<u>No.</u> <u>Copies</u>
M. L. Robertson Manager, Electrochemical and Power Sonics Division Naval Weapons Support Center Crane, Indiana 47522	1	Dr. T. Marks Department of Chemistry Northwestern University Evanston, Illinois 60201
Dr. Elton Cairns Energy & Environment Division Lawrence Berkeley Laboratory University of California Berkeley, California 94720	1	Dr. D. Cipris Allied Corporation P. O. Box 3000R Morristown, New Jersey 07960
Dr. Micha Tomkiewicz Department of Physics Brooklyn College Brooklyn, New York 11210	1	Dr. M. Philpot IBM Corporation 5600 Cottle Road San Jose, California 95193
Dr. Lesser Blum Department of Physics University of Puerto Rico Rio Piedras, Puerto Rico 00931	1	Dr. Donald Sandstrom Washington State University Department of Physics Pullman, Washington 99164
Dr. Joseph Gordon, II IBM Corporation K33/281 5600 Cottle Road San Jose, California 95193	1	Dr. Carl Kannewurf Northwestern University Department of Electrical Engineering and Computer Science Evanston, Illinois 60201
Dr. Robert Somoano Jet Propulsion Laboratory California Institute of Technology Pasadena, California 91103	1	Dr. Edward Fletcher University of Minnesota Department of Mechanical Engineering Minneapolis, Minnesota 55455
Dr. Johann A. Joebstl USA Mobility Equipment R&D Command DRDME-EC Fort Belvoir, Virginia 22060	1	Dr. John Fontanella U.S. Naval Academy Department of Physics Annapolis, Maryland 21402
Dr. Judith H. Ambrus NASA Headquarters M.S. RTS-6 Washington, D.C. 20546	1	Dr. Martha Greenblatt Rutgers University Department of Chemistry New Brunswick, New Jersey 08903
Dr. Albert R. Landgrebe U.S. Department of Energy M.S. 6B025 Forrestal Building Washington, D.C. 20595	1	Dr. John Wassib Kings Mountain Specialties P. O. Box 1173 Kings Mountain, North Carolina 28086

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No.</u> <u>Copies</u>
Dr. J. J. Brophy University of Utah Department of Physics Salt Lake City, Utah 84112	1
Dr. Walter Roth Department of Physics State University of New York Albany, New York 12222	1
Dr. Thomas Davis National Bureau of Standards Polymer Science and Standards Division Washington, D.C. 20234	1
Dr. Charles Martin Department of Chemistry Texas A&M University	1
Dr. Anthony Sammells Institute of Gas Technology 3424 South State Street Chicago, Illinois 60616	1
Dr. H. Tachikawa Department of Chemistry Jackson State University Jackson, Mississippi 39217	1
Dr. W. M. Risen Department of Chemistry Brown University Providence, Rhode Island	1

N.
Cop

